

Continuous fixed bed adsorption studies of Rhodamine-B dye using polymer bound adsorbent

Gopal N^{1,*}, Asaithambi M¹, Sivakumar P² & Sivakumar V³

¹Department of Chemistry, Erode Arts College, Erode 638 008, TN, India

²Department of Chemistry, AA Govt Arts College, Namakkal 637 002, TN, India

³Department of Chemistry, Sri Vasavi College, Erode 638 316, TN, India

E-mail: chemgopal@yahoo.com

Received 11 September 2013; accepted 26 January 2014

An eco-friendly adsorbent is developed by coating polyaniline over an activated carbon prepared from the seeds of *Prosopis Juliflora* using $ZnCl_2$ as an activating agent (PPAC). The polymer bound adsorbent has good adsorption characteristics with a surface area of $1028 \text{ m}^2/\text{g}$. A continuous flow fixed bed study is carried out by using PPAC as an adsorbent packed in a column for the removal of Rhodamine-B dye from aqueous solution. The effect of operating parameters such as flow rate, bed height and inlet dye concentration on the sorption characteristics of RB have been investigated at room temperature (30°C) and the natural pH of dye solution. On increasing the influent concentration from 25 to 75 mg/L, the volume of effluent treated decreases from 3800 to 2950 mL. The kinetic models suggested by Bohart-Adam, Thomas and Yoon-Nelson are employed to study this adsorption system. The YN model fits exceptionally well for the adsorption of RB onto PPAC with respect to all of the calculated parameters with high correlation coefficient (0.9431 to 0.9668) and low standard deviation (0.04 to 0.75).

Keywords: *Prosopis Juliflora*, Activated carbon, Adsorption, Polyaniline, Rhodamine B

Violation of environmental ethics by the human community leads to severe consequences. Most of the wastes generated by human activities are simply discharged onto the environment without any treatment. Disposal of untreated wastes not only makes haphazard appearance and also produces so many diseases to human being, animals and plants as well. Dyes are group of compounds which are used for colouring in textile, tannery, printing and paint industries. Owing to their chemical structure, wastewater containing dye molecules are highly resistant to exposure to light and other chemical as well as biological treatment processes. Conventional treatment methods are inefficient to decolourize the dyeing industry effluent¹.

Application of adsorption using activated carbon for the treatment of industrial wastewater and also for the recovery of organic compounds finds growing interest². In general, the adsorption methods are used in the final stage in the industrial wastewater treatment^{3,4}. Adsorption using activated carbon is best suited method for the treatment of dye bearing wastewater. The high cost involved for the use of activated carbon limits its usage in the small scale industries particularly in the developing countries. The recent research in the surface

chemistry is to find an economically viable and easily available low-cost adsorbent from biologically waste products.

Plenty of agro based waste products have been evaluated for their capacity to adsorb heavy metals and dye pollutants present in the wastewater⁵⁻¹⁴. The information obtained from adsorption kinetics and isotherm in a batch mode is useful for the determination of the effectiveness of the adsorbent-adsorbate system. Fixed bed columns do not necessarily operate under equilibrium conditions because the contact time is not sufficiently long for the attainment of equilibrium.

The column adsorption process is an effective process for the treatment of dyeing industrial wastewater, the adsorbent can be effectively used to treat the effluent for better quality. Large volume of wastewater can be continuously treated using a limited quantity of adsorbent is also an added advantage. Besides, other operational problems such as uneven flow pattern in the column, recycling of the spent adsorbent and regeneration cannot be studied in batch experiments¹⁵.

Prosopis juliflora is a shrub or small tree in the Fabaceae family. The Mesquite tree grows to a height of up to 12 metres (39 ft) and has a trunk with a diameter

of up to 1.2 meters. A mature plant can produce hundreds to thousands of seeds. Seeds remain viable for up to 10 years. *Prosopis juliflora* has become an invasive weed in several countries where it was introduced. Livestock which consume excessive amounts of seed pods are poisoned. The wood of this plant is being used as a precursor for the commercial production of activated carbon. In this work an activated carbon was prepared from *Prosopis juliflora* seed using $ZnCl_2$ as a chemical activating agent. The prepared carbon was encapsulated with polyaniline matrix (PPAC) to improve the mechanical strength and also improve the abrasion resistance. The removal of Rhodamine-B (RB) dye using Polyaniline coated Prosopis Juliflora Activated Carbon (PPAC) in column adsorption process. Previously derived mathematical models were used to evaluate the column performance for various operating conditions.

Experimental Section

Preparation of adsorbent

Prosopis juliflora seed was used as a precursor for the preparation of activated carbon. The seeds were collected in and around Erode District, Tamilnadu, India and they were cut into pieces of 2 to 3 cm size, dried in sunlight for 5 days. The dried seeds were washed with distilled water and soaked in a boiling solution of 10% $ZnCl_2$ and kept aside at room temperature for 24 h. After 24 h the residue filtered, initially air dried for 2 days and then carbonized in muffle furnace at $400^\circ C$ for 15 min. The carbonized material was washed with plenty of distilled water to remove any residual $ZnCl_2$. The dried carbon powdered, sieved to a particle size of 300 to 500 μ and finally activated at $800^\circ C$ in a closed container.

The polyaniline was synthesized on *Prosopis juliflora* seed activated carbon surface, which was previously soaked in monomer aniline solution (0.2 M) for 12 h at room temperature followed by slow addition of chemical oxidants 0.5 M Ammonium persulphate in 1.5 M HCl at room temperature for 4 h.

The physico chemical characteristics of the activated carbon were studied as per the standard procedures^{16,17} are given in Table 1. Surface area of the activated carbon samples were measured at 77 K using N_2 gas sorption analyzer (Nova 1000, Quanta Chrome Corporation, USA).

Adsorbate preparation

A cationic dye Rhodamine-B with a molecular formula ($C_{28}H_{31}N_2O_3Cl$; mol. wt. 479; C.I No. 45170,

λ_{max} 554 nm, (E. Merck, India) was chosen as the adsorbate. A stock solution containing 1000 mg of the dye per litre was prepared by dissolving appropriate amount of dye (based on percentage purity) in double distilled water and was used to prepare the adsorbate solutions by appropriate dilution as required. The structure of Rhodamine-B is shown in Fig. 1.

Column studies

Fixed bed column studies were carried out using a glass column of 1.5 cm inner diameter and 40 cm length. The column was packed with the prepared adsorbent by keeping glass wool at top and bottom as shown in the Fig. 2. The adsorbate fed into the

Table 1 — Physico-chemical properties of PPAC

S.No	Properties	Values
1	pH	7.48
2	Conductivity, mS/cm ²	0.273
3	Moisture content, %	11.4
4	Ash, %	16.4
5	Volatile matter, %	15.5
6	Matter soluble in water, %	0.44
7	Matter soluble in 0.25 M HCl, %	1.27
8	Bulk density, (g / ml)	0.46
9	Specific Gravity	0.93
10	Porosity, %	50.54
11	Surface area, m ² / g	1028
12	Methylene blue value, mg/g	443

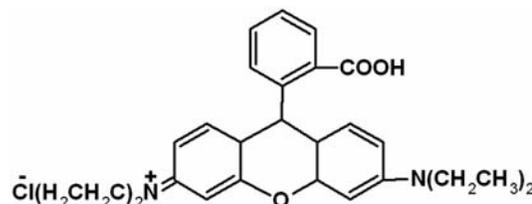


Fig. 1 — Structure of Rhodamine B

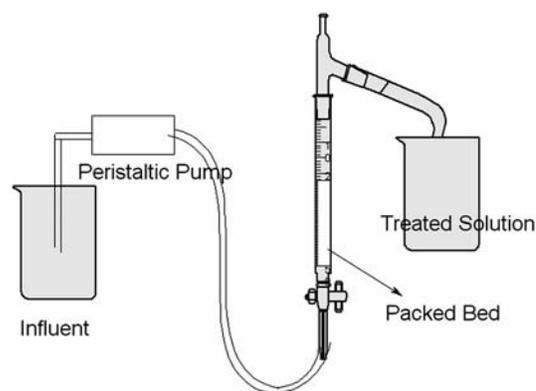


Fig. 2 — Flow Chart of the packed bed column

column through upflow method at specified rate using peristaltic pump. The effluent samples coming out of the column were collected at specified intervals and analysed for the residual dye concentration using (Elico Make) Bio UV-Vis spectrometer at a wavelength of 554 nm.

Theoretical background

Bohart-Adams Model

Oulman proposed the use of a bed depth service model for simulating granular activated carbon (GAC) adsorption beds¹⁸. The model, first developed by Bohart and Adams¹⁹, was based on surface reaction theory as given by Eq. (1)

$$\frac{C_0}{C} = \frac{1}{1 + e^{a-bt}} \quad \dots (1)$$

The Bohart-Adams equation is as follows:

$$\ln\left(\frac{C_0}{C} - 1\right) = \frac{KNx}{u} - KC_0t \quad \dots (2)$$

where, *C* is effluent concentration (mg/L); *C*₀ is influent concentration (mg/L);

K is adsorption rate coefficient (L/mg/min); *N* is adsorption capacity coefficient (mg/L); *x* is bed depth (cm); *u* is flow rate (mL/min); and *t* is time (min).

Thomas Model²⁰

The solid phase concentration of the dye on the adsorbent from the continuous mode studies can be well expressed by the Thomas model. The kinetic model suggested by Thomas is one of the widely used kinetic models for the evaluation of column performance. The Thomas model has the following form

$$\frac{C_t}{C_0} = \frac{1}{1 + \exp\left[k_T(q_{0(T)}m - C_0v)\right]/r} \quad \dots (3)$$

where,

*C*_{*t*} is effluent dye concentration (mg/L) at time *t*, *C*₀ is initial dye concentration (mg/L), *k*_{*T*} is Thomas rate constant, (L/min.mg), *q*_{0(*T*)} is maximum dye adsorption capacity (mg/g), *m* is mass of the adsorbent (g), *v* is effluent volume (mL) and *r* is flow rate (ml/min). The value of time, *t* = *v*/*r*.

The constants *k*_{*T*} and *q*₀ were determined from a plot of *C*_{*t*}/*C*₀ against *t* for a given set of conditions using non-linear regression analysis.

Yoon-Nelson Model²¹

Yoon and Nelson have proposed a less complicated model to represent the breakthrough of gases onto activated charcoal. The model was proposed based on the assumption that the rate of decrease in the probability of adsorption for each adsorbate molecule is proportional to the probability of adsorbate adsorption and the probability of adsorbate breakthrough on the adsorbent. The linear form of Yoon-Nelson model is

$$\ln\left(\frac{C_t}{C_0 - C_t}\right) = k_{YN}.t - \tau.k_{YN} \quad \dots (4)$$

where, *k*_{*YN*} is Yoon-Nelson rate constant, *τ* is the time required for 50% of adsorbate breakthrough and *t* is the sampling time. A plot of $\ln\left(\frac{C_t}{C_0 - C_t}\right)$ versus *t* gives a straight line with a slope of *k*_{*YN*} and intercept of $-\tau.k_{YN}$.

Based on Yoon-Nelson model, the amount of dye being adsorbed in a fixed bed is half of the total dye entering the adsorption bed within 2*τ* period²². For a given bed

$$q_{0YN} = \frac{q_{(total)}}{m} = \frac{\frac{1}{2}C_0[(r/1000) \times 2\tau]}{m} = \frac{C_0.r.\tau}{1000m} \quad \dots (5)$$

From this equation, the adsorption capacity, *q*_{0(*YN*)} varies as a function of inlet dye concentration (*C*₀), Flow rate (*r*), weight of adsorbent (*m*) and 50% breakthrough time.

Error analysis²³

The adsorption capacity obtained by the Thomas Model and Yoon-Nelson Model was compared with the experimental adsorption capacity using the following Error analysis method.

$$Sd = \sqrt{\sum \frac{(q_{0(exp)} - q_{0(cal)})^2}{N}} \quad \dots (6)$$

where, *q*_{0(*exp*)} is experimental adsorption capacity, *q*_{0(*cal*)} is the adsorption capacity calculated using Thomas and Yoon-Nelson kinetic models and *N* is the Number of experimental points run.

Results and Discussion

Effect of initial dye concentration

Results obtained for the adsorption of RB onto a column prepared from PPAC at various operating conditions are presented in Fig. 3. On increasing the influent concentration from 25 to 75 mg/L, the volume of effluent treated decreases from 3800 mL to 2950 mL as shown in Table 2. The number of solute molecules compete for the vacant sites of adsorbent increases on increasing the influent concentration, which results in quicker exhaustion of the column. The concentration gradient solid liquid interface is more at higher concentration which drives the solute molecules to enter into the adsorption sites. Though the volume of influent treated decreases with respect to influent concentration but the amount of dye removed from the solution is high at higher concentration.

The results obtained at various flow rate indicated that the influent flow rate also influences the quantities of dye removed. On increasing the flow rate from 5 to 15 mL/min at 50 mg/L of Initial dye concentration and 5 cm bed height the volume of dye solution treated decreases from 3700 to 2900 mL. At higher flow rates the contact time between the solute and the surface of adsorbent decreases which minimizing the possibilities of adsorbent-adsorbent interaction and results in reduced uptake of solute by the column. In-order to set an effective column for the solute adsorption it is essential to maximum contact time between the solute and sorbent. In this study 5 mL/min of flow rate gives maximum efficiency with 75.51 mg/g of solute removal.

The breakthrough curve reaches saturation at higher volume on increasing the bed height from 5 to 10 cm. This can be clearly observed that the system

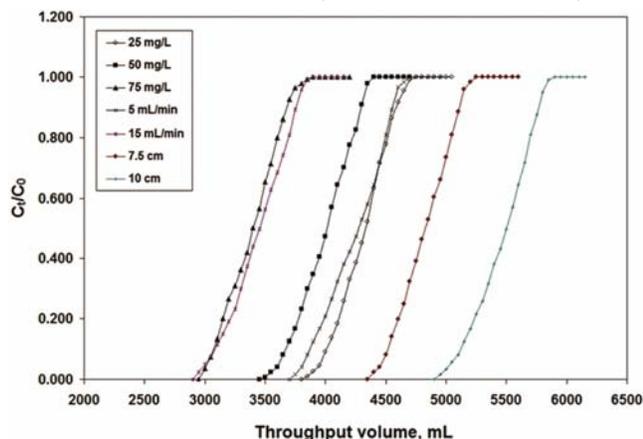


Fig. 3 — Breakthrough curve for the adsorption of RB onto PPAC

efficiency in terms of volume of dye solution treated increase with increase of bed height. Even a bed height of more than 10 cm can be tried to improve the efficiency but the size of adsorbent particles must be increased to avoid clogging. For this selected adsorbent-adsorbate system 10 cm bed height gives maximum efficiency without any operational difficulties.

Bohart-Adam Model

Many researches have applied the Bohart-Adam model equation directly to evaluate the adsorption system. In this work the amount of dye adsorbed mg/g was evaluated through the factor N (adsorption capacity coefficient in mg/L). This parameter was converted to adsorption capacity of the adsorbent packed in the column by considering the volume of dye solution treated with respect to the amount of adsorbent used. The Bohart-Adam model plot for the adsorption of RB onto PPAC is presented in Fig. 4.

The adsorption rate coefficient K decreases from 3.55×10^{-3} to 1.08×10^{-3} L/mg/min on increasing the influent concentration from 25 to 75 mg/L as given in Table 2. Adsorption rate coefficient is an indication of volume of influent treated by unit amount of adsorbent at unit time. On increasing the concentration more solute molecules form greater concentration gradient which ultimately reduces the adsorption rate coefficient. When the flow rate increased from 5 to 15 mL/min the adsorption rate coefficient decreases from 7.2×10^{-3} to 2.2×10^{-3} L/mg/min owing to the poor dwell time for the solute while increasing the bed depth from 5 to 10 cm.

The adsorption capacity coefficient (N) and its derivative adsorption capacity of the adsorbent (q_{BA})

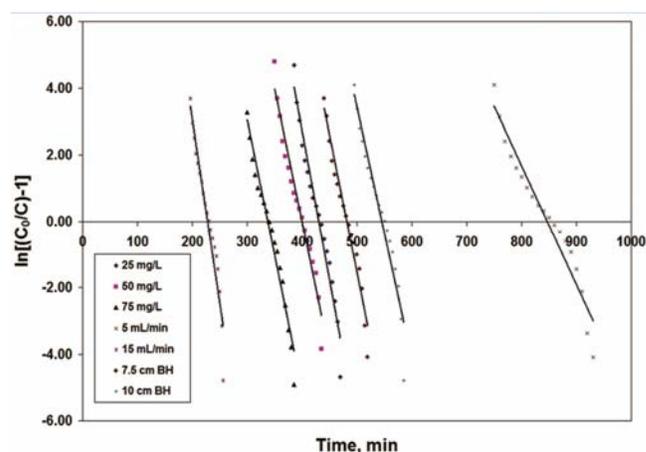


Fig. 4 — Bohart Adam model plot for the adsorption of RB onto PPAC

Table 2 — Results of various column adsorption models for the adsorption of RB onto PPAC column.

Concentration, mg/L		25	50	75	50	50	50	50
Flow Rate, mL/min		10	10	10	5	15	10	10
Bed height, cm		5	5	5	5	5	7.5	10
$q_{0 (exp)}$, mg/g		38.78	70.41	90.31	75.51	59.18	59.18	50.00
Breakthrough volume, mL		3800	3450	2950	3700	2900	4350	4900
Bohart – Adams Model Results	$K \times 10^{-3}$, L/mg/min	3.55	1.6	1.08	0.72	2.2	1.64	1.53
	N, mg/L	21.52	39.93	50.60	42.28	34.22	32.11	27.26
	$Q_{0(ba)}$, mg/g	28.20	47.51	51.47	53.94	34.22	32.11	23.03
	r^2	0.9681	0.9629	0.9668	0.9445	0.9437	0.9663	0.9431
	Sd	2.07	4.49	7.62	4.23	4.90	5.31	5.29
Thomas Model Results	$k_T \times 10^{-4}$, mL/min/mg	8.4	6.4	6.6	2.3	6.6	5.0	5.2
	$q_{0 (T)}$, mg/g	51.61	91.76	130.05	102.67	87.46	75.92	62.59
	r^2	0.8585	0.9324	0.9577	0.9124	0.9659	0.8594	0.8721
	Sd	2.52	4.19	7.79	5.33	5.55	3.28	2.47
Yoon Nelson Model Results	$k_{(YN)}$, L/min	0.09	0.08	0.11	0.04	0.11	0.08	0.08
	τ ,	429.89	399.33	337.34	845.60	228.11	481.59	545.12
	$q_{0(YN)}$, mg/g	37.06	68.85	87.24	72.90	58.99	55.36	46.99
	r^2	0.96	0.9629	0.9668	0.9445	0.9437	0.9663	0.9431
	Sd	0.34	0.31	0.60	0.51	0.04	0.75	0.59

increases while increasing the influent concentration from 25 to 75 mg/L. More availability of solute molecules on the adsorbent surface results in higher uptake of dye molecules by unit mass of adsorbent. The experimental and calculated adsorption capacity has moderate difference as evident from the high standard deviation values. The regression coefficient values are comparatively good enough to support the applicability of Bohart-Adam model for the adsorption of RB onto PPAC column.

Thomas Model

The mathematical model suggested by Thomas was applied for the adsorption of RB onto a column prepared using PPAC. The Thomas model parameters were calculated from the slope and intercept of the plot. The adsorption data at various initial dye concentration, flow rate and bed depth applied to Thomas model to determine the kinetic coefficients for the selected adsorbent-adsorbate system. The fitness of the data to the Thomas model was analysed using non-linear regression method (Fig. 5). The regression coefficients indicated that the model provides nominal fits to the experimental data with r^2 ranging from 0.8585 to 9577.

The adsorption capacity $q_{0(T)}$ increases from 51.61 to 130.05 mg/g on increasing the influent concentration from 25 to 75 mg/L. The adsorption capacity show a decrease trend while increasing the flow rate and bed depth. Though the bed depth increase enhances the quantity of treated effluent, but

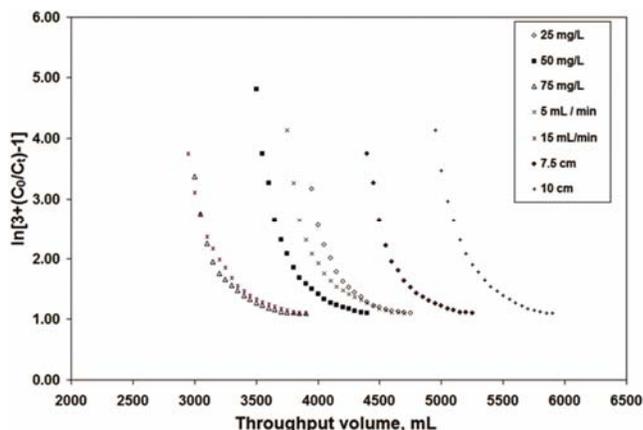


Fig. 5 — Thomas model plot for the adsorption of RB onto PPAC

the amount of solute per unit quantity of adsorbent decreases. The experimental adsorption capacity (q_{exp}) and the calculated value does not coincide very much, which may due the poor fit of the Thomas model. The high standard deviation also substantiates the poor fitness of Thomas model.

Yoon-Nelson Model

The Yoon-Nelson model rate constant (k_{YN}) and τ were determined from the slope and intercept of the YN model plot as shown in Fig. 6 and the results are presented in table 2. Out of the three models tested for the adsorption of RB onto PPAC column, the YN model provides excellent fit with very high r^2 and low Sd. For all the range of concentration under investigation, the calculated adsorption capacity and

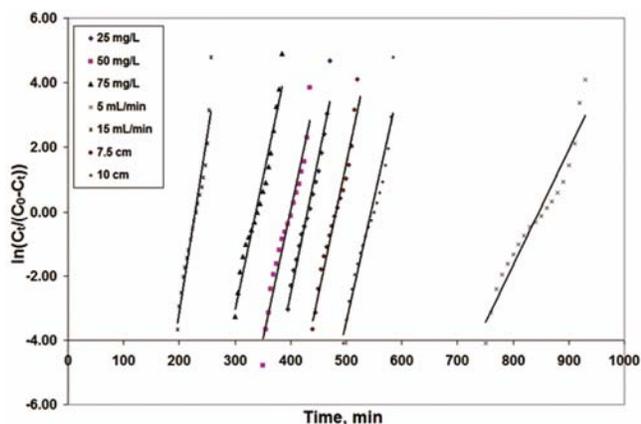


Fig. 6—Yoon-Nelson model plot for the adsorption of RB onto PPAC

the experimental adsorption capacity were very close, which substantiates the fitness of YN model.

The time required for 50% adsorbent breakthrough (τ) decreases on increasing the concentration. As the adsorbent get saturated quickly at higher concentration which leads to decrease of τ . The increase in flow rate decrease the value of τ from 845 to 228.11 correspondingly the value of dye solution treated decreases. Bed depth increase gives more and more adsorption sites there by increase the value of τ which in term increases quantity of treated dye effluent. The YN model fits exceptionally well for the adsorption of RB onto PPAC with respect to all of the calculated parameters.

Conclusion

An activated carbon with good adsorption characteristics is prepared successfully and employed for the adsorption of removal of RB from aqueous solution using packed bed column. The sorption of RB by PPAC carbon predominantly depends on the initial dye concentration, flow rate and also the height of packed column. The influent concentration increase causes quick exhaustion of the column and at the same time more solute molecules are removed per unit mass of the adsorbent. The three kinetic models

describes the adsorption of RB onto PPAC column well with good results. The Yoon-Nelson model gives an excellent fitness to the adsorption data and the parameters derived from this model has good correlation with the experimental results. Activated carbon prepared from *Prosopis Juliflora* seeds could be a promising adsorbent for the colour removal of textile industrial effluents.

References

- 1 Robinson T, Chandran B & Nigam P, *Bioresour Technol*, 85 (2002) 119.
- 2 Pelech R, Milchert E & Bartkowiak M, *J Colloid Interface Sci*, 296 (2006) 458.
- 3 Pelech R, Bemnowska A & Milchert E, *Pol J Chem Technol*, 3 (2001) 17.
- 4 Moreno-Castilla C, *Carbon*, 42 (2004) 83.
- 5 Macchi G, Marani D & Tirivanti G, *Environ Technol Lett*, 7 (1986) 431.
- 6 Suemitsu R, Uenishi R, Akashi I & Nakano M, *J Appl Polym Sci*, 31 (1986) 75.
- 7 Tan W T & Khan A R M, *Environ Technol Lett*, 9 (1988) 1223.
- 8 Maranon E & Sastre H, *Bioresour Technol*, 38 (1991) 39.
- 9 Okieimen F E, Okundia E U & Ogbefun D E, *J Chem Technol Biotechnol*, 51 (1991) 97.
- 10 Low K S, Lee C K & Lee K P, *Bioresour Technol*, 44 (1993) 109.
- 11 Marshall W E, Campagne E T & Evans W J, *J Environ Sci Health*, 28 (1993) 1977.
- 12 Namasivayam C & Periasamy K, *Water Res*, 27 (1993) 1663.
- 13 Tan W T, Ooi S T & Lee C K, *Environ Technol*, 14 (1993) 277.
- 14 Low K S, Lee C K & Leo A C, *Bioresour Technol*, 51 (1995) 227.
- 15 Queka S Y & Al-Duri B, *Chem Engg Proc*, 46 (2007) 477.
- 16 ISI, Activated Carbon, *Powdered and Granular—Methods of sampling and its tests*, (Bureau of Indian Standards, New Delhi), IS 877 – 1989.
- 17 APHA, *Standard Methods for the Examination of Water & Wastewater*, 15th edn., Washington, DC (1980).
- 18 Oulman C S, *J Am Water Works Assoc*, 72 (1) (1980) 50.
- 19 Bohart G S & Adams E Q, *J Chem Soc*, 42 (1920) 523.
- 20 Thomas H C, *J Am Chem Soc*, 66 (1944) 1664.
- 21 Yoon Y H & Nelson J H, *Am Ind Hyg Assoc J*, 45 (1984) 509.
- 22 Zumriye Aksu, Seyda Sen Cagatay & Ferda Gonen, *J Hazard Mater*, 143 (2007) 362.
- 23 Han R, Wang Y, Yu W, Zou W, Shi J & Liu H, *J Hazard Mater*, 141 (2007) 713.