



Optimization of wear parameters for aluminium 4% fly-ash composites

Subramaniam Magibalan^{a*}, Palanisamy Senthilkumar^b, Chinnamuthu Senthilkumar^c & Muthusamy Prabu^d

^{a,b,d}Department of Mechanical Engineering, K.S.R. College of Engineering, Tiruchengode 637215, India

^cDepartment of Mechanical Engineering, University College of Engineering, Panruti 607106, India

Received: 23 April 2019; Accepted: 11 March 2020

Dry sliding wear behaviour of aluminium matrix composites (AMCs) prepared by stir casting with 4% as fly ash reinforcement has been studied in the work. Dry sliding wear tests have been conducted using a pin-on-disc wear-testing machine to study the effect of changeable process parameters such as load, time, and sliding velocity, which have been used as design variables on the output parameters wear rate (WR) and coefficient of friction (COF). Sensitivity analysis has been carried out to find out the most significant parameter that can be controlled to minimize the WR. Further, the wear parameters have been optimized using the technique for order of preference by similarity to ideal solution (TOPSIS) approach to reduce the WR. Therefore, this study offers useful insights to composite manufacturers, especially for automotive industries.

Keywords: Aluminium Alloy 8011, Sensitivity analysis (SA), Response Surface Methodology (RSM), Wear rate (WR), TOPSIS

1 Introduction

Metal matrix composites (MMCs) have appear because of necessary group of material used in aerospace, transport and industry¹. The combined property of aluminium alloys with reinforcements increased the lifespan of the composite material, tensile with elevated temperature conditions². Many methods have been used for development and processing of aluminium particulate metal matrix composites to optimize the wear and mechanical properties is commonly done by various methods such as spray deposition^{3,4}, mechanical alloying^{5,6}, stir casting^{7,8} and direct metal laser sintering^{9,10}. These properties mainly depend on many factors such as composition of the aluminium alloy, fabrication method, type of ceramic reinforcements, distribution over the matrix alloy and wettability between matrix alloy and reinforcement¹¹⁻¹⁸.

Dhar *et al.*¹⁹ have studied the electrical discharge machining (EDM) of Al-4Cu-6Si alloy with 10 wt. % SiC_p composites and developed a second order, non-linear mathematical model for establishing the relationship among machining parameter and responses.

Kumar *et al.*²⁰ studied the AlB₂ particles reinforced in Al 8011 alloy by in-situ technique to synthesize Al8011/6 vol. % of AlB₂ composite. During synthesis, in-situ reaction takes place between molten alloy and inorganic salt KBF₄ at 850°C and it led to the formation of AlB₂.

Dey *et al.*²¹ have developed the mathematical model of AA6061/cenosphere. The process parameters and the mathematical model calculate all the responses such as cutting speed, kerf width and surface roughness. The Box Behnken is employed to analyze the effects of significant parameters on the performance characteristics.

Karaoglu *et al.*²² analyses the weld bead process parameters with different penetration to vary the input parameters as well as the welding process. The developed a mathematical equation of response surface methodology (RSM) for powder mixed electric discharge machining (PMEDM) as reported by Kansal *et al.*²³.

Gadakh²⁴ has investigated the TOPSIS technique for best possible parameter selection of wire electrical discharge(WED) machine process. Genetic algorithm (GA), artificial neural network (ANN) and grey relational analysis (GRA). Among these methods, TOPSIS techniques are very simply implemented and also quite useful for the decision makers. TOPSIS technique almost matches with any derived from the earlier period of researchers to provide evidence.

Nayak & Mahapatra²⁵ have used the TOPSIS technique on the multi-response optimization in wire electrical discharge machining(WEDM) and work piece material D₂ tool steel. The process parameters with responses material removal rate (MRR) and surface roughness (SR). The range of best possible

*Corresponding author (E-mail: magibalan42@gmail.com)

process parameters in the wire electrical discharge machining (WEDM) method by considering the experimental values are represented higher value MRR and lower value Ra.

Yuvaraj & Pradeep Kumar²⁶ have studied the multiple-criteria decision-making (MCDM) using the TOPSIS method in the abrasive water jet machine and work piece material AA5083-H32 aluminium alloy. The selected parameters are feed rate, current, pulse on-time, and the gap voltage. The experimental results show the level and parameter by using TOPSIS method to optimize several output responses in optimal conditions were reported by Manivannan & Kumar²⁷.

Lakshminarayanan *et al.*²⁸ have conducted the experiments with three factors and three level and central composite design (CCD) with full factorial SA to predict the tensile strength of friction stir welded alloy AA7039 aluminium.

Senthilkumar and Kannan²⁹ have conducted the sensitivity analysis of arc welding material of super duplex stainless steel. This technique used insignificant coefficient values removed to create reduced models in machining parameters. Based on the results they concluded the sensitivity analysis to use to identify the important parameter and properties of the deposited layer.

Munda & Bhattacharyya³⁰ have created a RSM models for higher-order processes are analyzed using three methods namely TOPSIS, base component analysis, and GRA. TOPSIS provides the top results as reported by Gauriet *al.*³¹.

In the present work, an attempt is pin-on-disc equipment is accustomed to investigate the dry sliding wear behaviour of the composite (AA8011-4 wt.-% fly ash) using multi criteria decision-making methods TOPSIS. In the group of this background, the present paper was conducted.

2 Experimental Method

2.1 Selection of Materials and Testing

AA8011 base material of Chemical composition shows that Fe 0.65%, Si 0.70%, Zn 0.10%, Cu 0.10%, Ti 0.08, Cr 0.05%, Mg 0.05%, Al98.07% and the reinforcement exact chemical composition of fly ash SiO₂ 65.93%, Al₂O₃ 23.69%, CaO 3.93 %, Fe₂O₃ 2.83%, K₂O 2.77%, Na₂O 0.86%. The separation of Al MMCs use in this study is carried out by stir casting technique. Al in the form of sheet and the reinforcement materials in the form of particulates are used for trials³²⁻³⁵.

2.2 Dry Sliding Wear Test

Figure 1 shows the ASTM Standard-G99 with Pin on Disc machine (Model: DUCOM TR20) was used to conduct the wear test at an atmospheric temperature. Circular specimen 10 mm diameter and 50 mm height were machined from the castings. In this present work, WR and coefficient of friction were identified as the output and the WR was calculated by Eq. (1).

$$\text{Wear rate (g/min)} = \frac{(\text{metal removed from part})}{(\text{Time of machining})} \quad \dots(1)$$

2.3 Development of Mathematical Model for Wear Rate

CCD method used on RSM full factorial design with Orthogonal Array 20 support to three level and three factor experimental was selected and the input parameter are load, time, sliding velocity are given in Table 1. The calculated WR and COF for all the 20 experiments are given in Table 2. In Eq. (2) formulate the RSM modelling related with response Y_a Response surface modelling is accustomed establish the applied mathematics relationship between the response (Y_a) and therefore the numerous machining parameters was calculated by Eq. (2)³²⁻³⁵.



Fig. 1 — Pin-on-disc setup.

Table 1 — Process parameters and their levels.

PARAMETERS	LEVEL		
	-1	0	1
Normal Load (N)	5	10	15
Time (min)	5	10	15
Sliding velocity (m/s)	1.5	3	4.5

$$Y_a = b_a + \sum_{m=1}^k b_k x_k + \sum_{k=1}^k b_{kk} x_k^2 + \sum_{l>1}^k b_{kl} x_k x_l \dots (2)$$

where,

Y_a is the response and the x_k (1, 2... etc) are coded level of k numerical variables.

b_a is the endless term on constant value

b_k is linear term

b_{kk} is quadratic terms

b_{kl} is interaction terms.

3 Results and Discussion

3.1 TOPSIS using Wear Characteristics on AA8011-4% Fly-Ash Composite

Step 1: The normalize matrix for AA8011-4% Fly ash is given in Table 3 and it follows the Eq. (3) as given below.

$$R_{ab} = x_{ab} / (\sum x_{ab}^2) \dots (3)$$

for $a = 1 \dots m, b = 1 \dots n$

Step 2: The sum of allocated weights for given WR and COF should be equal to one (where $WR = 0.50$ and $COF = 0.50$).

Step 3: In order to optimize decision matrix, the weighted normalized decision matrix Eq. (4) is constructed, and the weights for each criterion, w_b for $b = 1 \dots n$.

$$Y_{ab} = W_b R_{ab} \dots (4)$$

Table 2 — Wear characteristics of AA 8011- 4% fly- ash composite.

S.No.	Load (N)	Time (min)	Sliding velocity (m/s)	Wear rate (g/min) × 10 ⁻³	COF (μ)
1	5	5	1.5	0.342	0.559
2	15	5	1.5	0.434	0.372
3	5	15	1.5	0.372	0.497
4	15	15	1.5	0.484	0.542
5	5	5	4.5	0.428	0.369
6	15	5	4.5	0.534	0.334
7	5	15	4.5	0.454	0.266
8	15	15	4.5	0.585	0.452
9	5	10	3	0.422	0.523
10	15	10	3	0.535	0.523
11	10	5	3	0.398	0.344
12	10	15	3	0.434	0.375
13	10	10	1.5	0.380	0.383
14	10	10	4.5	0.466	0.249
15	10	10	3	0.430	0.382
16	10	10	3	0.435	0.38
17	10	10	3	0.434	0.384
18	10	10	3	0.430	0.386
19	10	10	3	0.432	0.384
20	10	10	3	0.432	0.382

To obtain the element, normalized decision matrix for each column is multiplied by its respective weight. Table 4 shows the weighted normalized matrix.

Step 4: Determine the positive ideal and negative ideal solution the following Eqs (5) & (6) are used.

For positive solution,

$$A^+ = \{Y_a^+, \dots, Y_n^+\} \dots (5)$$

where,

$$Y_a^+ = \{ \max(Y_{ab}) \text{ if } b \in J, \min(Y_{ab}) \text{ if } b \in J' \}$$

For negative solution,

$$A^- = \{Y_b^-, \dots, Y_n^-\} \dots (6)$$

where

$$Y_b^- = \{ \min(Y_{ab}) \text{ if } b \in J, \max(Y_{ab}) \text{ if } b \in J' \}$$

$$Y^+ = 0.1465 Y^+ = 0.1514$$

$$Y^- = 0.0856 Y^- = 0.0674$$

Step 5: The solution to the determination of the separation measure from the ideal alternative solution Eq. (7) is presented in Table 5.

$$S_i^+ = [\sum (Y_a^+ - Y_{ab})^2]^{1/2} \dots (7)$$

Similarly, the solution for the determination of the separation measure from the negative solution is Eq. (8) is presented in Table 5.

$$S_i^- = [\sum (Y_a^- - Y_{ab})^2]^{1/2} \dots (8)$$

Table 3 — Normalized matrix.

Ex. No	Wear rate (g/min) × 10 ⁻³	COF (μ)
1	0.1713	0.3027
2	0.2173	0.2015
3	0.1863	0.2692
4	0.2424	0.2935
5	0.2143	0.1998
6	0.2674	0.1809
7	0.2273	0.1441
8	0.2929	0.2448
9	0.2113	0.2832
10	0.2679	0.2832
11	0.1993	0.1863
12	0.2173	0.2031
13	0.1903	0.2074
14	0.2334	0.1349
15	0.2153	0.2069
16	0.2178	0.2058
17	0.2173	0.2080
18	0.2153	0.2091
19	0.2163	0.2080
20	0.2163	0.2069

Step 6: With regard to the relative closeness coefficient calculation the Eq. (9) of a particular alternative, the results are presented in Table 6.

$$P_i = S_i^- / (S_i^+ + S_i^-) \quad \dots(9)$$

$0 < P_i < 1$: Select the option with P_i closest to 1

From Table 6, the relative closeness coefficient value of each experimental run is known. By using TOPSIS, the experiment number 14 (Load: 10 N, Time: 10 min, Sliding Velocity: 4.5 m/s) shows the maximum closeness coefficient and explains that the ideal value is the nearest value for the corresponding experiment. The variation in closeness value of each experimental run can be observed from Figure 2.

Figure 3 highlights the percentage contribution of individual parameter and it is evident from the

Table 4 — Weighted normalized matrix.

Ex. No	Wear rate (g/min) × 10 ⁻³	COF(μ)
Weights	0.50	0.50
1	0.0856	0.1514
2	0.1087	0.1007
3	0.0931	0.1346
4	0.1212	0.1468
5	0.1072	0.0999
6	0.1337	0.0904
7	0.1137	0.0720
8	0.1465	0.1224
9	0.1057	0.1416
10	0.1340	0.1416
11	0.0997	0.0932
12	0.1087	0.1015
13	0.0951	0.1037
14	0.1167	0.0674
15	0.1077	0.1034
16	0.1089	0.1029
17	0.1087	0.1040
18	0.1077	0.1045
19	0.1082	0.1040
20	0.1082	0.1034

Table 5 — Separation measures of ideal and negative ideal solution matrix.

Ex. No	S+	S-
1	0.1037	0.0000
2	0.0504	0.0557
3	0.0858	0.0184
4	0.0833	0.0359
5	0.0510	0.0558
6	0.0264	0.0776
7	0.0332	0.0842
8	0.0550	0.0674
9	0.0847	0.0223
10	0.0753	0.0493
11	0.0535	0.0599
12	0.0510	0.0549
13	0.0629	0.0486
14	0.0298	0.0895
15	0.0530	0.0528
16	0.0517	0.0538
17	0.0526	0.0527
18	0.0537	0.0518
19	0.0530	0.0525
20	0.0526	0.0530

Table 6 — Relative closeness coefficient.

S. No	Relative Closeness	Rank
1	0.0004	20
2	0.5247	6
3	0.1768	19
4	0.3011	17
5	0.5223	7
6	0.7466	2
7	0.7175	3
8	0.5508	4
9	0.2085	18
10	0.3959	16
11	0.5285	5
12	0.5187	8
13	0.4360	15
14	0.7501	1
15	0.4991	12
16	0.5100	9
17	0.5005	11
18	0.4909	14
19	0.4977	13
20	0.5018	10

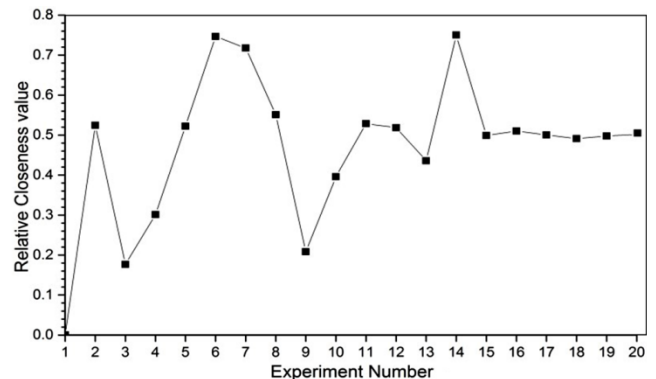


Fig. 2 — Experimental numbers versus Relative closeness coefficient.

observation that sliding velocity 67% and load 32% are the major domination parameter and time is 1% is the least significant parameter (Table 7).

3.2 Optimization of Wear Characteristics using AA8011-4% Fly ash composite

Table 2 gives the experimental results for the characteristics of dry sliding wear for AA8011-4% Fly ash composite and the maximum value for WR (g/min) × 10⁻³ is 0.466 and minimum value for COF is 0.249 μ with the load of (10 N), Time (10 min) and sliding velocity (4.5 m/s). TOPSIS technique used in optimizing, WR and COF value is very near to the experimental value and is selected from Table 8.

The WR (g/min) × 10⁻³ is 0.476 gm/min and the predicted parameters are load 10.8 N, Time 11 min and sliding velocity 4.8 m/s. A new experiment is

designed and conducted with the optimum values of the wear parameters by predicting the response from the optimum condition.

In Table 9 shows the evaluation of predicted machining operation with actual machining operation is made to get results and a good agreement has been obtained between these operations. The residues are studied from the validation test a result of WR is found to be within the permissible limit.

3.2 Sensitivity Analysis

Sensitivity analysis the non-significant terms are eliminate response Eq. (10) for WR are given below.

$$WR (g/min) \times 10^{-3} = 0.31731 - 0.03017 A + 0.01441 B + 0.04885 C + 0.001867 A^2 - 0.000633 B^2 - 0.003919 C^2 + 0.000225 AB + 0.000550 AC \dots (10)$$

Sensitivity analysis the non-significant terms are eliminate response Eq. (11) for COF are given below

$$COF (\mu) = 0.97512 - 0.14661 A + 0.00639 B + 0.10816 C + 0.005475 A^2 - 0.001065 B^2 - 0.031172 C^2 + 0.002265 AB + 0.004883 AC - 0.001550 BC \dots (11)$$

Eqs 10 & 11 differentiating with high opinion to three parameters of Load (A), Time (B), and Sliding velocity (C) are given below.

$$\frac{dWR}{dA} = -0.03017 + 0.001867 * 2A + 0.000225 B + 0.000550 C \dots (12)$$

$$\frac{dCOF}{dA} = -0.14661 + 0.005475 * 2A + 0.002265 B + 0.004883 C \dots (13)$$

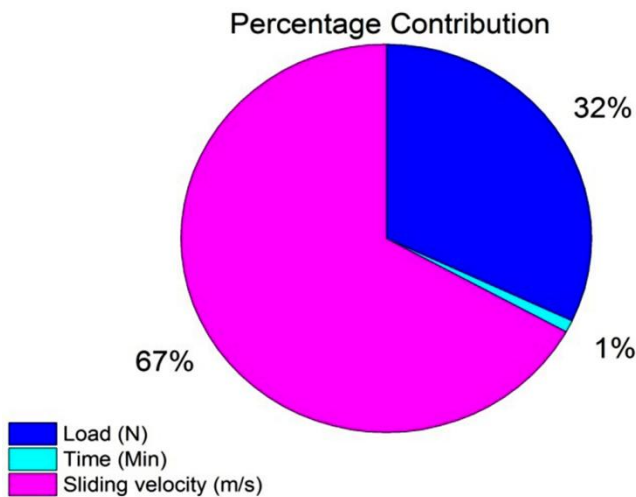


Fig. 3 — Percentage contributions of individual parameters.

Table 7— ANOVA using AA8011-4% fly -ash composite.

S. No.	Parameters	DOF	Sum of squares	Mean square	F value	Percentage contribution (%)
1	Load (N)	2	0.178292	0.08915	9.30	32
2	Time (Min)	2	0.003182	0.00159	0.17	1
3	Sliding velocity (m/s)	2	0.370036	0.18502	19.31	67

Table 8 — Optimal values of Wear rate using AA8011-4% fly- ash composite.

Ex. No.	Load (N)	Time (min)	Sliding Velocity (m/s)	Wear rate (g/min) × 10 ⁻³	COF (μ)
14	10	10	4.5	0.466	0.249

Table 9 — Validation test results for Wear rate using AA8011-4% fly -ash composite.

Ex. No.	Load (N)	Time (min)	Sliding Velocity (m/s)	Wear rate (g/min) × 10 ⁻³		
				Predicted	Actual	%Error
1	10.8	11	4.8	0.476	0.468	2.53

$$\frac{dWR}{dB} = 0.01441 - 0.000633 * 2 B + 0.000225 \quad \dots (14)$$

$$\frac{dCOF}{dB} = 0.00639 - 0.001065 * 2 B + 0.002265 A - 0.001550 C \quad \dots (15)$$

$$\frac{dWR}{dC} = 0.04885 - 0.003919 * 2 C + 0.000550 A \quad \dots (16)$$

$$\frac{dCOF}{dC} = 0.10816 - 0.031172 * 2 C + 0.004883 A - 0.001550 B \quad \dots (17)$$

Eqs (12-17) two responses (WR and COF) for sensitivities equation of load, time, sliding velocity is mentioned in Tables 10 & 11.

Figure 4 shows the load at 5-15 N of sensitivity analysis for WR and COF. At 5 N the WR and COF is negative value after increases the load 10 N and 15 N the sensitivity analysis for WR and COF on negative value.

Figure 5 shows the time at 5-15 min of sensitivity analysis for WR and COF. At 5 min the WR and COF is positive value after increases the time 10 min and 15 min the sensitivity analysis for WR and COF on positive value.

Figure 6 shows the sliding velocity at 1.5-4.5 m/s of sensitivity analysis for WR and COF. At 1.5 m/s and 3 m/s sliding velocity of the WR and COF is positive value after increases the sliding velocity at 4.5 m/s the sensitivity analysis for WR and COF on positive value.

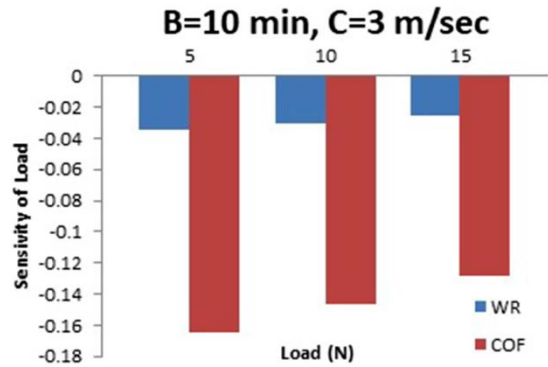


Fig. 4 — Sensitivity analysis results of load.

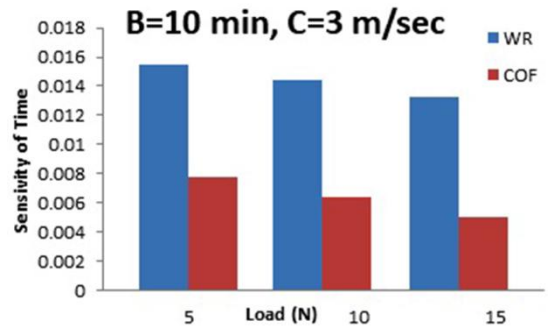


Fig. 5 — Sensitivity analysis results of time.

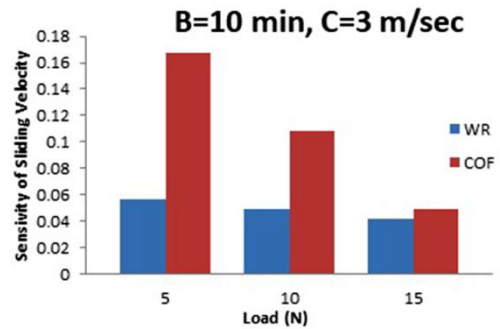


Fig. 6 — Sensitivity analysis results of sliding velocity.

Table 10 — Wear rate for sensitivities of process parameters.

Load (N)	B=10 min, C=3 m/sec		
	$\frac{dWR}{dA}$	$\frac{dWR}{dB}$	$\frac{dWR}{dC}$
5	-0.0347	0.0155	0.0562
10	-0.0302	0.0144	0.0489
15	-0.0257	0.0133	0.0415

Table 11 — COF for sensitivities of process parameters.

Load (N)	B=10 min, C=3 m/sec		
	$\frac{dCOF}{dA}$	$\frac{dCOF}{dB}$	$\frac{dCOF}{dC}$
5	-0.1647	0.0078	0.1672
10	-0.1466	0.0064	0.1082
15	-0.1285	0.005	0.0491

4 Conclusions

- (i) Optimization of AA 8011 with 4 wt.-% of fly ash composite has been carried out using TOPSIS for all experiments. The optimized values obtained through TOPSIS have close agreement with the experimental values.
- (ii) The relative closeness coefficient value 0.7501 of each experimental run is known by using TOPSIS, the experiment number 14 (Load: 10 N, Time: 10 min, Sliding Velocity: 4.5 m/s) shows the maximum closeness coefficient and explains that the ideal value is the nearest value for the corresponding experiment.
- (iii) TOPSIS technique used in optimizing the dry sliding wear for AA8011- 4 % Fly ash composite and the maximum value for WR (g/min) $\times 10^{-3}$ is 0.466 and minimum value for COF is 0.249 μ with the load of (10 N), Time (10 min) and sliding velocity (4.5 m/s).
- (iv) The WR (g/min) $\times 10^{-3}$ value is 0.476 gm/min and the predicted parameters are load 10.8 N, Time 11 min and sliding velocity 4.8 m/s. The predicted machining operation with actual machining operation is made to get results and a good agreement has been obtained between these operations. The residues are studied from the validation test results of WR are found to be within the permissible limit.

References

- 1 Suresh S, Shenbaga Vinayaga Moorthi N, Vettivel SC & Selvakumar N, *Mater Des*, 59 (2014) 383.
- 2 Huda MD, Hashmi MSJ & El-Baradie MA, *Key Eng Mater*, 104 (1995) 37.
- 3 Chen ZH, Zhan MY & Xia WJ, *Mater Sci Technol*, 20 (2004) 1621.
- 4 Wang F, Liu H & Yang B, *Mater Character*, 54 (2005) 446.
- 5 Arik H, Ozcatalbas Y & Turker M, *Mater Des*, 27 (2006) 799.
- 6 Lu L, Lai MO, Wu CF & Breach C, *J Metastable Nanocryst Mater*, 6 (1999) 357.
- 7 Shorowordi KM, Haseeb ASMA & Celis JP, *Wear*, 261(2006) 634.
- 8 Celis J-P, Ponthiaux P & Wenger F, *Wear*, 261 (2006) 939.
- 9 Ganesh R, Saranesh Kumar J, Satya Prakash R & Chandrasekaran K, *ApplMech Mater*, 787 (2015) 588
- 10 Ghosh SK & Saha P, *Mater Des*, 32 (2011) 139.
- 11 Amanov A, Sasaki S, Kim D, Penkov OV & Pyun Y, *TribolInt* 64 (2013) 24.
- 12 Basavarajappa S, Chandramohan G, & Paulo Davim J, *Mater Des* 28 (2007) 1393.
- 13 Natarajan S, Narayanasamy R, Kumares Babu SP, Dinesh G, Anil Kumar B & Sivaprasad K, *Mater Des*, 30 (2009) 2521.
- 14 Straffellini G, Bonollo F, Molinari A & Tiziani A, *Wear*, 211 (1997) 192.
- 15 Alidokht SA, Abdollah-zadeh A & Assadi H, *Wear*, 305 (2013) 291.
- 16 Tjong S, *Mater Sci Eng R*, 29 (2000) 49.
- 17 Das S, *Trans Indian Inst Met*, 57 (2004) 325.
- 18 Rohatgi P, *JOM*, 43(1991)10.
- 19 Shankar BL, Anil K & Karabasappagol PJ, *IOP Conf Ser.: Mater Sci Eng*, 149 (2016) 012060.
- 20 Kumar N, Singh SK, Gautam G, Padap AK, Mohan A & Mohan S, *Mater Res Exp*, 4 (2017) 106514.
- 21 Dey A, Bandi VRR & Pandey KM, *Mater Today: Proc*, 5 (2018) 1278.
- 22 Bhattacharyya B, Gangopadhyay S & Sarkar BR, *J Mat Process Technol*, 189 (2007) 169.
- 23 Kansal HK, Singh S & Kumar P, *J Mater Process Technol*, 169 (2005) 427.
- 24 Gadakh VS, *Adv Prod Eng Manage*, 7 (2012) 157.
- 25 Nayak BB & Mahapatra SS, *Eng Sci Technol*, 19 (2016) 161.
- 26 Yuvaraj N & Pradeep Kumar M, *Mater Manuf Processes*, 30 (2014) 882.
- 27 Manivannan R & Kumar MP, *J Mech Sci Technol*, 30 (2016) 137.
- 28 Lakshminarayanan AK & Balasubramanian V, *Trans Nonferrous Met Soc China*, 19 (2009) 9.
- 29 Senthilkumar B, Kannan T, *Procedia Eng*, 64 (2013) 1030.
- 30 Munda J & Bhattacharyya B, *Int J Adv Manuf Technol*, 35 (2006) 821.
- 31 Gauri SK, Chakravorty R & Chakraborty S, *Int J Adv Manuf Technol*, 53 (2010) 1115.
- 32 Magibalan S, Senthilkumar P, Palanivelu R, Senthilkumar C, Shivasankaran N & Prabu M, *Mat Res Exp*, 5 (2018) 056505.
- 33 Magibalan S, Senthilkumar P, Senthilkumar C, Palanivelu R & Prabu M, *Mater Testing* 60 (2018) 209.
- 34 Magibalan S, Senthilkumar P, Senthilkumar C, Palanivelu R & Prabu M, *Mater Testing*, 60 (2018) 777.
- 35 Magibalan S, Senthilkumar P, Senthilkumar C, Palanivelu R & Prabu M, *Mater Testing*, 60 (2018) 765.